

Magneto-Optical Response Enhanced by Mie Resonances in Nanoantennas

Maria G. Barsukova,[†] Alexander S. Shorokhov,[†] Alexander I. Musorin,[†] Dragomir N. Neshev,^{‡, ID} Yuri S. Kivshar,[‡] and Andrey A. Fedyanin^{*,†, ID}


[†]Faculty of Physics, Lomonosov Moscow State University, Moscow 119991, Russia

[‡]Nonlinear Physics Centre, Research School of Physics and Engineering, Australian National University, Canberra ACT 2601, Australia

S Supporting Information

ABSTRACT: We demonstrate both experimentally and numerically multifold enhancement of magneto-optical effects in sub-wavelength dielectric nanostructures with a magnetic surrounding exhibiting localized magnetic Mie resonances. We employ amorphous silicon nanodisks covered with a thin nickel film and achieve the 5-fold enhancement of the magneto-optical response of the hybrid magnetophotonic array of nanodisks in comparison with a thin nickel film deposited on a flat silica substrate. Our findings allow for a new basis for active and nonreciprocal photonic nanostructures and metadevices, which could be tuned by an external magnetic field.

KEYWORDS: Mie resonances, silicon nanophotonics, subwavelength nanostructures, optical magnetism, magneto-optical effects

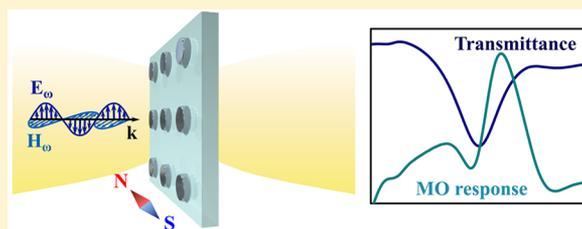

Control of light by an external magnetic field is one of the important methods for modulation of its intensity and polarization.¹ Magneto-optical effects at the nanoscale are usually observed in magnetophotonic crystals,^{2–5} nanostructured hybrid materials,^{6–9} or magnetoplasmonic crystals.^{10–18} The early studies on the enhancement of magneto-optical response in nanostructured materials were done more than 30 years ago.^{19–22} An indirect action of an external magnetic field (e.g., through the Faraday effect) is explained by the fact that natural materials exhibit negligible magnetism at optical frequencies. However, the concept of metamaterials overcome this limitation imposed by nature by designing artificial subwavelength meta-atoms that support a strong magnetic response, usually termed as optical magnetism, even when they are made of nonmagnetic materials.²³ The fundamental question is what would be the effect of the interaction between an external magnetic field and an optically induced magnetic response of metamaterial structures.²⁴ Here we make the first experimental step toward answering this fundamental question and demonstrate the multifold enhancement of the magneto-optical response of nanoantenna lattices due to the optical magnetism.

Nanophotonics is often associated with plasmonic structures made of metals such as gold or silver. However, it is known that plasmonic structures suffer from high losses of metals, heating, and incompatibility with CMOS fabrication processes. Recent developments in the nanoscale optical physics gave birth to a new branch of nanophotonics aiming at the manipulation of optically induced Mie-type resonances in dielectric nanoparticles made of materials with high refractive indices.^{23,25–27} It has been shown recently that resonant dielectric structures

offer unique opportunities for reduced dissipative losses and large resonant enhancement of both electric and magnetic fields. High-index dielectric structures can be employed as new building blocks to obtain unique functionalities such as magnetic Fano resonances,^{28,29} highly transmittable metasurfaces,^{33,34} and novel metadevices.^{35,36} Here we extend the concept of high-index resonant nanophotonics to the case of magnetically active materials and study the magneto-optical (MO) response of a dielectric array of nanodisks covered with a thin magnetic film, as shown schematically in Figure 1. We emphasize that at the microscopic level the optical response is driven by electric dipoles, but high-index dielectric nanoparticles with this microscopic response generate effectively magnetic multipoles. Despite its geometrical simplicity, a nanoantenna is a resonant element that supports both electric and magnetic multipolar modes that can generate efficiently optical magnetism effects. We employ such effects here and demonstrate, for the first time to our knowledge, that the optical magnetism associated with the magnetic dipole Mie resonance in a single silicon nanodisk leads to the multifold enhancement of the magneto-optical response of the hybrid magnetophotonic array of nanodisks in comparison with a thin nickel film deposited on a flat silica substrate.

We consider samples composed of a thin nickel film deposited on top of an array of silicon nanodisks with different diameters and study optical and magneto-optical response of such hybrid planar nanostructures. Nickel has been chosen as

Received: July 17, 2017

Published: September 14, 2017

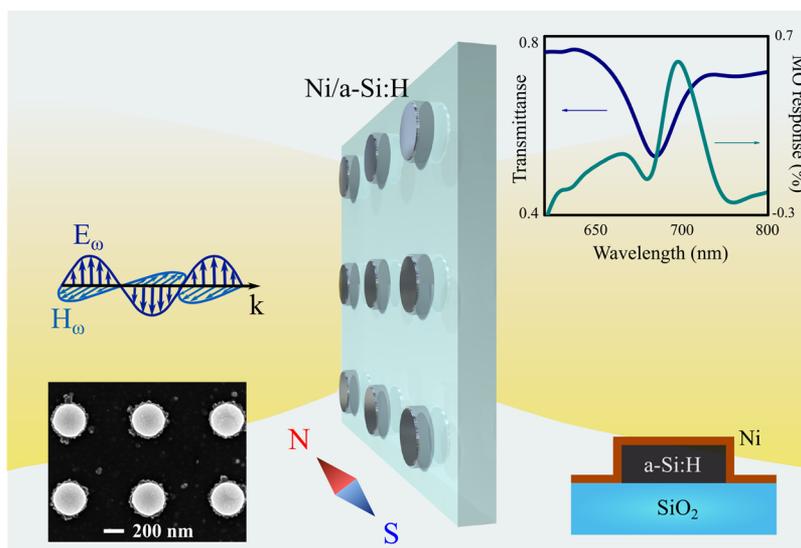


Figure 1. Schematic illustration of the enhancement of magneto-optical effects in a nanoscale structure. Linearly polarized light is focused on a dielectric metasurface composed of silicon nanoparticles supporting magnetic Mie-type resonances, the metasurface is covered by a thin nickel film. The sample is subjected to the action of an external magnetic field oriented perpendicular to the wave vector of the incident light. Inset shows an SEM image of the sample.

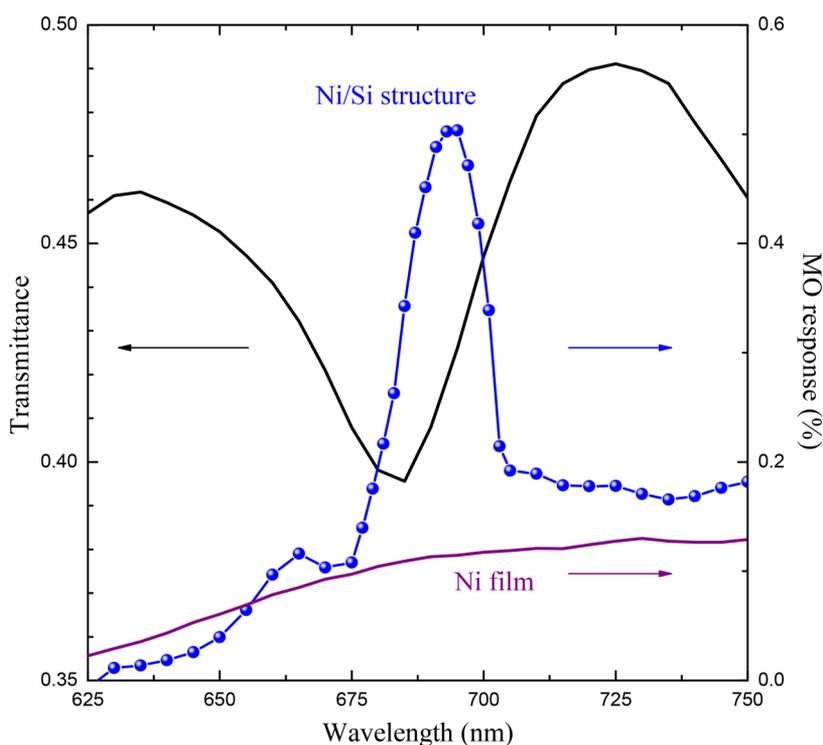


Figure 2. Experimental transmission (black, solid) and magneto-optical response (blue, circles). Sample comprises an array of silicon nanodisks with diameter $d = 340$ nm, height $h = 220$ nm, and lattice spacing $a = 830$ nm covered with a 5 nm thick Ni film. The purple line illustrates the magneto-optical response of the reference nickel film.

magnetic material because it has a high magnetic activity and possesses strong magnetic response, as it has been shown in the recent works.^{30–32} We also examined for comparison dielectric magnetic materials like yttrium iron garnet, and carried out the numerical simulations for the structure, where the 5 nm thick nickel film is replaced by the 5 nm-thick Bi:YIG film (see Supporting Information, “Comparison of magneto-optical responses of the structure in case of garnet and nickel film” section). Our results show that magneto-optical enhancement

for the structure with YIG film is 65× smaller than for the same sample with Ni film. Moreover, fabrication process for samples with YIG may affect the nanostructured a-Si disks, because YIG films must be annealed under high temperatures to become magneto-optically active. In addition with the aim of confirming the high efficiency and low losses of the considering structure we performed numerical calculation of the absorption coefficient for both structure under study and all-dielectric structure without Ni film (see Supporting Information, “Nickel

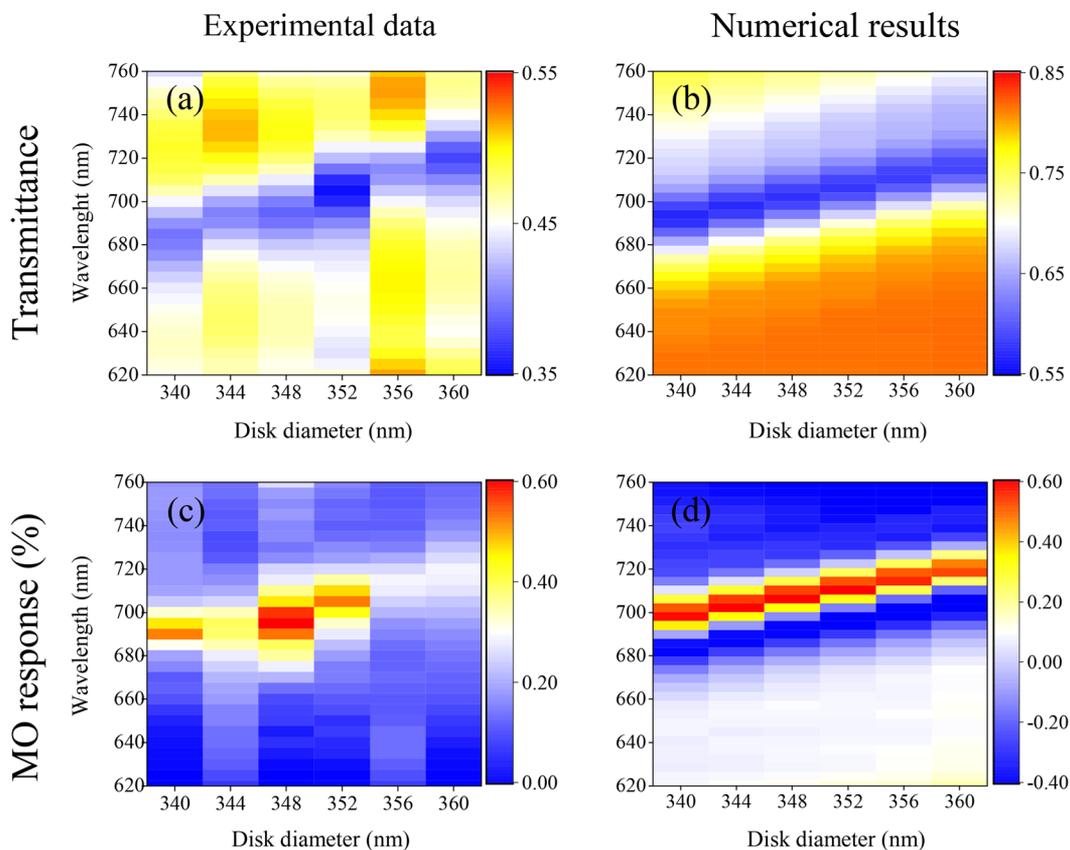


Figure 3. Control of the spectral position of the MO enhancement. (a, b) Experimental and numerical transmittance spectra respectively for nanodisks with different diameters. (c, d) Experimental and numerical magneto-optical response spectra.

film contribution to the absorption of the structure” section). The 5 nm thick Ni film changes the absorption for only 10–15% in comparison with the structure without Ni film. The shape of the nanodisks is chosen to match the position of the lowest Mie-type resonances. Indeed, it has been shown that the electric and magnetic dipolar resonances can be overlapped spectrally by changing both height and diameter of the nanodisk,³³ leading to a significant increase of the local fields inside a dielectric nanoscale structure.

For experimental studies, we use arrays of hydrogenated amorphous silicon nanodisks placed on a transparent silica substrate. The sample is covered with the 5 nm-thick nickel film in order to achieve the magneto-optical response in an external magnetic field. The SEM image of the sample is shown on Figure 1. The disk diameter d varies from 320 to 360 nm and the height of the nanodisks h is fixed, being equal to 220 nm. The magnetic dipole Mie resonance of an isolated nanoantenna is designed to be in the visible and near-IR spectral ranges. The lattice spacing a of the array is 830 nm, so that the contribution of diffraction is minimal because the phase-matching condition of the first diffraction maximum is satisfied only for the IR part of the spectrum due to the sample geometry. The contribution of higher-order resonances is negligible.

In experiment, we use normal incidence illumination and apply an external magnetic field along the sample surface and perpendicularly to the wave vector (see Figure 1). The incoming polarization is chosen to satisfy the right-hand rule: the electric field is perpendicular to both wave vector and direction of external magnetic field. This configuration is known as the Voigt geometry for transmission measurements.¹

The experimental geometry is similar to that used for the observation of the transverse magneto-optical Kerr effect (TMOKE), being an intensity-dependent effect observed for reflectance. An external magnetic field changes the refractive index of a magnetic medium. This action leads to a shift of the transmittance spectrum $\Delta\lambda$ relative to the nonmagnetized case. The MO response of the sample can be defined as following: $[T(H) - T(-H)]/T(0)$, where T is the transmittance and H is the applied external magnetic field. If the spectral shift is small ($\Delta\lambda \ll \lambda$, λ stands for the central wavelength of the resonance), the MO response is proportional to the spectral derivative of the transmittance, $\partial T/\partial\lambda$. It means that the maximum of the MO signal does not coincide with a dip or a peak in the transmission spectrum, but it corresponds to a maximal slope of the resonance curve. TMOKE is odd in the magnetization and could be observed for an oblique incidence: the sign of the effect changes with changing the angle of the incidence θ to $-\theta$ or reversing magnetic field direction. In the case of normal incidence, the MO response becomes weaker because it is proportional to the square of the magnetization. Due to this, the MO signal in the experiment is locked-in to the doubled frequency of an alternating external magnetic field.

In order to characterize optically our MO samples, we perform measurements of the transmittance with the setup described in the Methods section (Experimental Setup). Figure 2 shows the experimental results for one of the samples. The sample parameters are $a = 830$ nm, $d = 340$ nm, and $h = 220$ nm. The dip in the transmission at the wavelength of 685 nm corresponds to the excitation of the magnetic dipole Mie-type resonance in a single silicon nanodisk, which has been

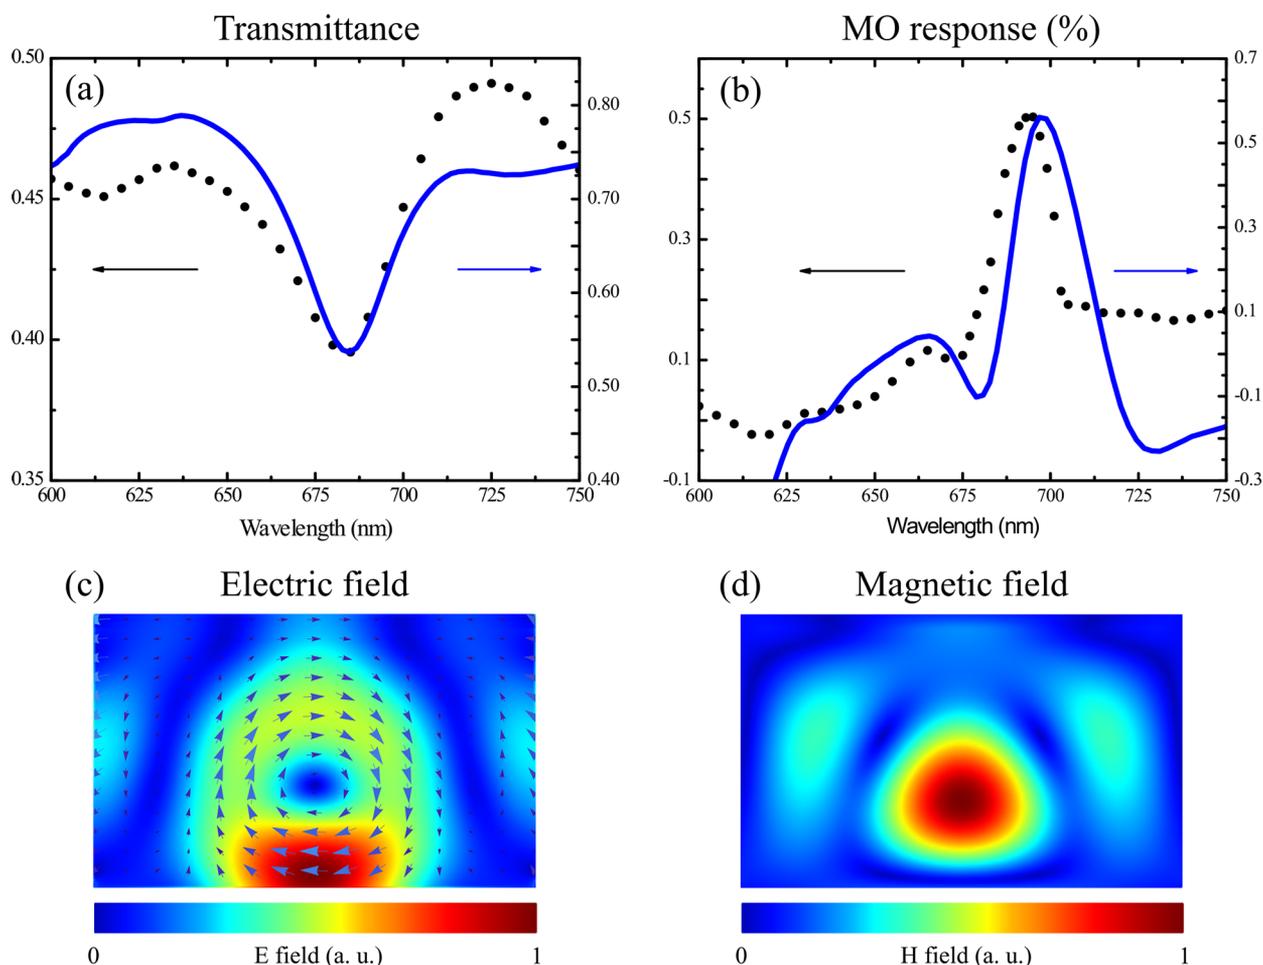


Figure 4. Comparison between experimental data and numerical results. Experimental (black dots) and numerical (blue solid lines) transmittance spectra (a) and magneto-optical response spectra (b) for an array of silicon nanodisks with a diameter of $d = 344$ nm, a height of $h = 220$ nm, and a lattice spacing $a = 830$ nm, covered with a 5 nm thick nickel film. (c, d) Calculated electric and magnetic fields inside the nanoantenna in the vicinity of the dipole magnetic Mie resonance at $\lambda = 680$ nm.

confirmed by numerical simulations (see Figures 3 and 4). The magneto-optical response shows a resonant enhancement in the vicinity of magnetic dipole resonance of the nanodisks (blue curve). The dependence of the magneto-optical effect on the magnitude of the applied external magnetic field is shown in Supporting Information. The magneto-optical response from the reference thin nickel film deposited on the silica substrate is illustrated in Figure 2 by a purple solid curve. The magneto-optical spectrum measured for the nickel film does not have any resonant features compared to the sample. Thus, we can easily trace the correlation between the magneto-optical enhancement and the dipole magnetic resonance excitation in the silicon nanodisks.

In order to confirm this idea, we fabricate a set of samples with increasing diameters of the silicon nanodisks. Depending on the disk diameter, the resonant wavelength is shifted: the wider the disk the redder the resonant wavelength. Figure 3 shows the spectral dependencies of the transmittance (a) and the MO response (b) for samples with different diameters of the nanodisks.

We observe the resonance shifts from the wavelength of 680 nm (for $d = 340$ nm) to 720 nm (for $d = 360$ nm). The corresponding shift of the MO response is illustrated in Figure 3c. To confirm our experimental data, we calculate the transmittance and MO response spectra using the finite-

difference time-domain (FDTD) technique in the Lumerical FDTD Solutions software (see Methods, Numerical Simulations). In our simulations, the refractive index of glass, the complex dielectric permittivity of Si disks, and the Ni film are all taken into account.

The comparisons between experimental results and numerical simulations are shown in Figure 4. Upper graphs illustrate experimental and numerical results for (a) transmittance and (b) magneto-optical response, for an array of silicon nanodisks with a diameter $d = 344$ nm, a height of $h = 220$ nm, and a lattice spacing $a = 830$ nm, covered with a 5 nm thick nickel film. The experimental and numerical spectra show quite similar behavior, but they differ in the absolute values. This difference could be caused by the local imperfections in the form and size of nanoparticles and the roughness of the deposited Ni film, which could bring about additional scattering losses and lead to a decrease in the transmission and magneto-optical response. The lower graphs in Figure 4 demonstrate the calculated (c) electric and (d) magnetic fields inside the nanodisk in the vicinity of the transmission dip, near 680 nm. These graphs confirm the magnetic nature of the excited Mie resonance. We also compared the contributions to the magneto-optical enhancement for the cases of electric and magnetic dipole resonances (see Supporting Information, “Comparison of magneto-optical responses stimulated by

magnetic and electric dipole resonances" section). Numerical results demonstrate that the magneto-optical effect enhancement caused by the magnetic dipole resonance excitation is several times stronger than in the case of the electric dipole resonance. Despite the fact that amplification of the local electric and magnetic fields in the region of magnetic and electric dipole resonances is comparable in magnitude, and also the slope of the resonance curve (see Figure S2 in the Supporting Information) in the vicinity of the electric dipole resonance exceeds the slope for the magnetic dipole resonance, the enhancement of the magneto-optical response is several times larger in the region of magnetic dipole resonance in comparison with the electric one. These results prove that magneto-optical effects are not only driven by the simple local field concentration in the nanoresonators, but also depend on the mode character.

In summary, we offer the first demonstration of the magneto-optical effects enhanced by optically induced magnetic dipole Mie resonances, manifesting a strong interaction between magnetic properties and induced optical magnetism. Our unique findings allow for novel approaches in a magnetic control of recently reported strong nonlinear effects in nanoparticles,³⁷ as well as the realization of the time-reversal symmetry breaking at the nanoscale for photonic topological insulators.³⁸ Our results could create a new basis for novel active and nonreciprocal nanophotonic structures and meta-devices, which could be tuned by external magnetic fields.

METHODS

Fabrication of Samples. In the capacity of a base material for our nanodisks, we use a 220 nm-thick hydrogenated amorphous silicon film deposited atop a silica substrate, using plasma-enhanced chemical vapor deposition technique in the Oxford PlasmaLab System 100. The deposition is carried out under the following conditions: 25 sccm SiH₄ and 475 sccm He at 250 °C for approximately 10 min. In order to nanostructure Si films, we use the electron-beam lithography with the subsequent reactive ion etching. For that purpose we spin-coat over the sample the negative tone ma-N-2403 electron beam resist with a thickness of 300 nm and a water-soluble anticharging conductive polymer (ESPACER 300Z) to avoid static charging. Then we expose the resist using an electron-beam lithography system Raith 150 and remove the anticharging layer in deionized water. The exposed film is developed in ma-D-525 for 80 s and brought to a reactive ion etching machine (Versaline LL ICP etching system). The etching process has been conducted in coupled plasma of SF₆ and CHF₃. After that, we deposit a thin nickel film on top of the sample surface using magnetron sputtering method. An SEM picture of one of the samples is shown in the inset to Figure 1.

Experimental Setup. Optical and magneto-optical spectra for the sample are measured with linearly polarized light from a halogen lamp, passing through a monochromator with spectral resolution of 3 nm. After a collimating system, a 150 μm aperture and a Glan-Taylor polarizer the radiation is focused at the normal incidence to the sample surface with a beam diameter of approximately 100 μm. The light transmitted through the sample is collected and directed to a Hamamatsu photomultiplier tube via an optical fiber. The signal is detected by a lock-in amplifier at an optical chopper's frequency of 131 Hz. Magneto-optical experiments were conducted without a chopper. The reference frequency of the lock-in amplifier is set

as a doubled frequency of the external alternating 300 Oe magnetic field (117 Hz). The orientation of the external magnetic field is perpendicular to the wave vector of the incident light.

Numerical Simulations. The optical response of the sample is calculated by using the finite-difference time-domain method in the Lumerical FDTD Solutions software. In our simulations, the complex dielectric permittivity of the Ni film and Si disks as a function of frequency is taken from the standard dispersion data.³⁹ The refractive index of the glass substrate is set constant 1.45 over the whole spectral range. In order to achieve the transmittance spectrum of the sample, we model an array of silicon disks covered with a 5 nm-thick Ni film and placed on a semi-infinite glass substrate, and illuminate it at the normal incidence by a plane wave, polarized perpendicularly to the magnetization. The calculated transmission spectrum is normalized to the power of the plane wave source. We use the periodic boundary conditions along both *x* and *y* axis and perfectly matched layers (PML) on the top and bottom of the unit cell to prevent parasitic interference. In order to obtain the magneto-optical response spectrum, the nondiagonal complex permittivity tensor of the Ni film is taken into account. Unitary transformation makes a permittivity tensor diagonalized with eigenvalues, and the Cartesian electric field components are converted into circularly polarized light according to the permittivity tensor. The MO response is defined as following: $2 \cdot [T(H) - T(0)]/T(0)$, where *T* is the transmittance and *H* is the external magnetic field.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/acsp Photonics.7b00783.

Additional experimental data and numerical method description (PDF).

AUTHOR INFORMATION

Corresponding Author

*E-mail: fedyanin@nanolab.phys.msu.ru.

ORCID

Dragomir N. Neshev: 0000-0002-4508-8646

Andrey A. Fedyanin: 0000-0003-4708-6895

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

The authors are grateful to M. Shcherbakov, T. Dolgova, A. Ezhov, and B. Luk'yanchuk for fruitful discussions, S. Evlashin for a help with nickel film deposition, S. Dagesyan for the help with the SEM characterization, and A. Frolov for a technical assistance with the experimental setup. This work was supported by the Russian Ministry of Education and Science (# 14.W03.31.0008; experiment), the Russian Foundation for Basic Research (Grant Nos. 16-32-00146, 16-32-00265 and 17-02-01286; modeling), and the Australian Research Council. Calculations and measurements have been performed in Lomonosov Moscow State University. This work was performed in part at the ACT node of the Australian National Fabrication Facility, a company established under the National

Collaborative Research Infrastructure Strategy to provide nano and microfabrication facilities for Australia's researchers.

REFERENCES

- (1) Buschow, K. H. J. *Handbook of Magnetic Materials*; Elsevier, 2003; Vol. 15.
- (2) Inoue, M.; Fujikawa, R.; Baryshev, A.; Khanikaev, A.; Lim, P. B.; Uchida, H.; Aktsipetrov, O.; Fedyanin, A.; Murzina, T.; Granovsky, A. Magnetophotonic crystals. *J. Phys. D: Appl. Phys.* **2006**, *39*, R151.
- (3) Goto, T.; Dorofeenko, A. V.; Merzlikin, A. M.; Baryshev, A. V.; Vinogradov, A. P.; Inoue, M.; Lisyansky, A. A.; Granovsky, A. B. Optical Tamm states in one-dimensional magnetophotonic structures. *Phys. Rev. Lett.* **2008**, *101*, 113902.
- (4) Musorin, A. I.; Sharipova, M. I.; Dolgova, T. V.; Inoue, M.; Fedyanin, A. A. Ultrafast Faraday Rotation of Slow Light. *Phys. Rev. Appl.* **2016**, *6*, 024012.
- (5) Romodina, M. N.; Soboleva, I. V.; Musorin, A. I.; Nakamura, Y.; Inoue, M.; Fedyanin, A. A. Bloch-surface-wave-induced Fano resonance in magnetophotonic crystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2017**, *96*, 081401.
- (6) Temnov, V. V.; Armelles, G.; Woggon, U.; Guzatov, D.; Cebollada, A.; Garcia-Martin, A.; Garcia-Martin, J.-M.; Thomays, T.; Leitenstorfers, A.; Bratschitsch, R. Active magneto-plasmonics in hybrid metal-ferromagnet structures. *Nat. Photonics* **2010**, *4*, 107–111.
- (7) Wang, L.; Clavero, C.; Huba, Z.; Carroll, K. J.; Carpenter, E. E.; Gu, D.; Lukaszew, R. A. Plasmonics and enhanced magneto-optics in core-shell Co-Ag nanoparticles. *Nano Lett.* **2011**, *11*, 1237–1240.
- (8) Mikhaylovskiy, R. V.; Hendry, E.; Secchi, A.; Mentink, J. H.; Eckstein, M.; Wu, A.; Pisarev, R. V.; Kruglyak, V. V.; Katsnelson, M. I.; Rasing, Th.; Kimel, A. V. Ultrafast optical modification of exchange interactions in iron oxides. *Nat. Commun.* **2015**, *6*, 8190.
- (9) Maksymov, I. S. Magneto-plasmonic nanoantennas: Basics and applications. *Rev. Phys.* **2016**, *1*, 36–51.
- (10) Grunin, A. A.; Zhdanov, A. G.; Ezhov, A. A.; Ganshina, E. A.; Fedyanin, A. A. Surface-plasmon-induced enhancement of magneto-optical Kerr effect in all-nickel subwavelength nanogratings. *Appl. Phys. Lett.* **2010**, *97*, 261908.
- (11) Jeong, H. J.; Kim, D.; Song, J. H.; Jeong, K. Y.; Seo, M. K. Resonant magneto-optic Kerr effects of a single Ni nanorod in the Mie scattering regime. *Opt. Express* **2016**, *24* (15), 16904–16912.
- (12) Belotelov, V. I.; Akimov, I. A.; Pohl, M.; Kotov, V. A.; Kasture, S.; Vengurlekar, A. S.; Gopal, A. V.; Yakovlev, D. R.; Zvezdin, A. K.; Bayer, M. Enhanced magneto-optical effects in magnetoplasmonic crystals. *Nat. Nanotechnol.* **2011**, *6*, 370–376.
- (13) Chin, J. Y.; Steinle, T.; Wehler, T.; Dregely, D.; Weiss, T.; Belotelov, V. I.; Stritzker, B.; Giessen, H. Nonreciprocal plasmonics enables giant enhancement of thin-film Faraday rotation. *Nat. Commun.* **2013**, *4*, 1599.
- (14) Maksymov, I. S. Magneto-plasmonics and resonant interaction of light with dynamic magnetisation in metallic and all-magneto-dielectric nanostructures. *Nanomaterials* **2015**, *5*, 577–613.
- (15) Bossini, D.; Belotelov, V. I.; Zvezdin, A. K.; Kalish, A. N.; Kimel, A. V. Magnetoplasmonics and femtosecond opto-magnetism at the nanoscale. *ACS Photonics* **2016**, *3*, 1385–1400.
- (16) Armelles, G.; Cebollada, A.; Garcia-Martin, A.; González, M. U. Magnetoplasmonics: combining magnetic and plasmonic functionalities. *Adv. Opt. Mater.* **2013**, *1* (1), 10–35.
- (17) Chesnitskiy, A. V.; Gayduk, A. E.; Prinz, V. Y. Transverse Magneto-Optical Kerr Effect in Strongly Coupled Plasmon Gratings. *Plasmonics* **2017**, 1–5.
- (18) Shcherbakov, M. R.; Vabishchevich, P. P.; Frolov, A. Yu.; Dolgova, T. V.; Fedyanin, A. A. Femtosecond intrapulse evolution of the magneto-optic Kerr effect in magnetoplasmonic crystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2014**, *90* (1), 201405.
- (19) Hui, P. M.; Stroud, D. Theory of Faraday rotation by dilute suspensions of small particles. *Appl. Phys. Lett.* **1987**, *50*, 950.
- (20) Ferguson, P. E.; Stafstudd, O. M.; Wallis, R. F. Enhancement of the transverse Kerr magneto-optic effect by surface magnetoplasma waves. *Physica B+C* **1977**, *89*, 91–94.
- (21) Krinchik, G. S.; Chepurova, E. E.; Kraeva, T. I. Excitation of magnetized-plasma surface waves in nickel. *JETP Lett.* **1984**, *40*, 776–780.
- (22) Inoue, M.; Isamoto, K.; Yamamoto, T.; Fujii, T. Magneto-optical Faraday effect of discontinuous magnetic media with a one-dimensional array structure. *J. Appl. Phys.* **1996**, *79* (3), 1611–1624.
- (23) Kuznetsov, A. I.; Miroshnichenko, A. E.; Brongersma, M. L.; Kivshar, Y. S.; Luk'yanchuk, B. Optically resonant dielectric nanostructures. *Science* **2016**, *354*, aag2472.
- (24) De Sousa, N.; Froufe-Pérez, L. S.; Sáenz, J. J.; García-Martín, A. Magneto-Optical Activity in High Index Dielectric Nanoantennas. *Sci. Rep.* **2016**, *6*, na.
- (25) Kuznetsov, A. I.; Miroshnichenko, A. E.; Fu, Y. H.; Zhang, J.; Luk'yanchuk, B. Magnetic light. *Sci. Rep.* **2012**, *2*, 492.
- (26) Evlyukhin, A. B.; Novikov, S. M.; Zywiets, U.; Eriksen, R. L.; Reinhardt, C.; Bozhevolnyi, S. I.; Chichkov, B. N. Demonstration of Magnetic Dipole Resonances of Dielectric Nanospheres in the Visible Region. *Nano Lett.* **2012**, *12*, 3749–3755.
- (27) Decker, M.; Staude, I. Resonant dielectric nanostructures: a low-loss platform for functional nanophotonics. *J. Opt.* **2016**, *18*, 1–31.
- (28) Hopkins, B.; Filonov, D. S.; Miroshnichenko, A. E.; Monticone, F.; Alù, A.; Kivshar, Y. S. Interplay of Magnetic Responses in All-Dielectric Oligomers To Realize Magnetic Fano Resonances. *ACS Photonics* **2015**, *2*, 724–729.
- (29) Shorokhov, A. S.; Melik-Gaykazyan, E. V.; Smirnova, D. A.; Hopkins, B.; Chong, K. E.; Choi, D. Y.; Shcherbakov, M. R.; Miroshnichenko, A. E.; Neshev, D. N.; Fedyanin, A. A.; Kivshar, Y. S. Multifold enhancement of third-harmonic generation in dielectric nanoparticles driven by magnetic Fano resonances. *Nano Lett.* **2016**, *16*, 4857–4861.
- (30) Bonanni, V.; Bonetti, S.; Pakizeh, T.; Pirzadeh, Z.; Chen, J.; Nogués, J.; Vavassori, P.; Hillenbrand, R.; Åkerman, J.; Dmitriev, A. Designer magnetoplasmonics with nickel nanoferrromagnets. *Nano Lett.* **2011**, *11* (12), 5333–5338.
- (31) Chen, J.; Albella, P.; Pirzadeh, Z.; Alonso-González, P.; Huth, F.; Bonetti, S.; Bonanni, V.; Åkerman, J.; Nogués, J.; Vavassori, P.; Dmitriev, A.; Aizpurua, J.; Hillenbrand, R. Plasmonic nickel nanoantennas. *Small* **2011**, *7* (16), 2341–2347.
- (32) Valev, V. K.; Silhanek, A. V.; Gillijns, W.; Jeyaram, Y.; Paddubrouskaya, H.; Volodin, A.; Biris, C. G.; Panoiu, N. C.; De Clercq, B.; Ameloot, M.; Aktsipetrov, O. A.; Moshchalkov, V. V.; Verbiest, Th. Plasmons reveal the direction of magnetization in nickel nanostructures. *ACS Nano* **2011**, *5* (1), 91–96.
- (33) Staude, I.; Miroshnichenko, A. E.; Decker, M.; Fofang, N. T.; Liu, S.; Gonzales, E.; Dominguez, J.; Luk, T. S.; Neshev, D. N.; Brener, I.; Kivshar, Y. Tailoring Directional Scattering through Magnetic and Electric Resonances in Subwavelength Silicon Nanodisks. *ACS Nano* **2013**, *7*, 7824–7832.
- (34) Decker, M.; Staude, I.; Falkner, M.; Dominguez, J.; Neshev, D. N.; Brener, I.; Pertsch, T.; Kivshar, Y. S. High-Efficiency Dielectric Huygens' Surfaces. *Adv. Opt. Mater.* **2015**, *3*, 813–820.
- (35) Kruk, S.; Hopkins, B.; Kravchenko, I. I.; Miroshnichenko, A.; Neshev, D. N.; Kivshar, Y. S. Broadband highly efficient dielectric metadevices for polarization control. *APL Photonics* **2016**, *1*, 030801.
- (36) Genevet, P.; Capasso, F.; Aieta, F.; Khorasaninejad, M.; Devlin, R. Recent advances in planar optics: from plasmonic to dielectric metasurfaces. *Optica* **2017**, *4*, 139–152.
- (37) Shcherbakov, M. R.; Neshev, D. N.; Hopkins, B.; Shorokhov, A. S.; Staude, I.; Melik-Gaykazyan, E. V.; Decker, M.; Ezhov, A. A.; Miroshnichenko, A. E.; Brener, I.; Fedyanin, A. A.; Kivshar, Y. S. Enhanced Third-Harmonic Generation in Silicon Nanoparticles Driven by Magnetic Response. *Nano Lett.* **2014**, *14*, 6488–6492.
- (38) Lu, L.; Joannopoulos, J. D.; Soljčić, M. Topological states in photonic systems. *Nat. Phys.* **2016**, *12*, 626–629.
- (39) Palik, E. D. *Handbook of Optical Constants of Solids*; Academic Press: Boston, 2012.